

# Toward the automatic deflection analysis in historic timber slabs by combining 3D point clouds and machine learning approaches

## *Hacia el análisis automático de deformaciones en forjados de madera históricos mediante la combinación de nubes de puntos 3D e inteligencia artificial*

Pablo Sanz-Honrado<sup>ID</sup>

Rubén Santamaria-Maestro<sup>ID</sup>

J. Ramón Aira-Zunzunegui<sup>ID</sup>

Paula Villanueva-Llauradó<sup>ID</sup>

Luis Javier Sánchez-Aparicio<sup>ID</sup>

Institute of Physical and Information Technologies Leonardo Torres Quevedo (ITEFI), CSIC, Madrid. España. [pablo.sanz@csic.es](mailto:pablo.sanz@csic.es)

Dept. of Construction and Technology in Architecture (DCTA), Escuela Técnica Superior de Arquitectura, Universidad Politécnica de Madrid, Madrid. España. [ruben.santamaria.maestro@upm.es](mailto:ruben.santamaria.maestro@upm.es)

Dept. of Construction and Technology in Architecture (DCTA), Escuela Técnica Superior de Arquitectura, Universidad Politécnica de Madrid, Madrid. España. [joseramon.aira@upm.es](mailto:joseramon.aira@upm.es)

Dept. of Building Structures and Physics, Escuela Técnica Superior de Arquitectura, Universidad Politécnica de Madrid, Madrid. España. [paula.villanueva@upm.es](mailto:paula.villanueva@upm.es)

Dept. of Construction and Technology in Architecture (DCTA), Escuela Técnica Superior de Arquitectura, Universidad Politécnica de Madrid, Madrid. España. [lj.sanchez@upm.es](mailto:lj.sanchez@upm.es)

Autor de contacto: [pablo.sanz@csic.es](mailto:pablo.sanz@csic.es)

### ABSTRACT

In the field of Cultural Heritage, 3D point clouds are pivotal for representing scenes with high resolution and accuracy. Although traditionally used for planimetries and computational modelling, this study explores their potential in diagnostics. A novel methodology is proposed that leverages 3D point clouds to evaluate deflection in historic timber slabs. By combining Artificial Intelligence with advanced 3D point cloud techniques, an approach is developed for detecting beam deflections with high precision. Specifically, a multi-resolution Random Forest classifier identifies beams and their faces, while deflection is computed using connected component and minimum bounding rectangle algorithms. Applied to timber slabs in the Nuestra Señora convent in Ávila. This methodology demonstrates promising results, achieving 99% accuracy in beam detection and a high degree of automation in deflection assessment. This approach offers significant advancements in the diagnostic capabilities of 3D point clouds in heritage conservation.

**Keywords:** diagnostics; laser scanner; artificial intelligence; timber floors; point cloud.

### RESUMEN

*Las nubes de puntos 3D son una fuente clave de información geométrica para el estudio y documentación del patrimonio construido, especialmente en la generación de planimetrías y modelos tridimensionales. Este artículo explora su potencial más allá de la representación visual, proponiendo una metodología innovadora para el análisis automatizado de deformaciones en forjados tradicionales de madera. La propuesta combina técnicas de inteligencia artificial, mediante el uso del algoritmo Random Forest para la identificación de los elementos constructivos, con algoritmos específicos orientados a la evaluación geométrica de las deflexiones de los forjados. La metodología ha sido validada en un caso de estudio real —el Convento de Gracia en Ávila, mostrando resultados prometedores y un alto grado de automatización. En conjunto, la investigación aporta avances significativos en el uso de las nubes de puntos 3D como herramienta de diagnóstico estructural en patrimonio arquitectónico.*

**Palabras clave:** diagnóstico; escáner láser; inteligencia artificial; forjados de madera; nube de puntos.

**Cómo citar este artículo/Citation:** Pablo Sanz-Honrado, Rubén Santamaria-Maestro, José Ramón Aira-Zunzunegui, Paula Villanueva-Llauradó, Luis Javier Sánchez-Aparicio (2025). Toward the automatic deflection analysis in historic timber slabs by combining 3D point clouds and machine learning approaches. Informes de la Construcción, 77 (580): 7096. <https://doi.org/10.3989/ic.7096>

**Copyright:** © 2025 CSIC. This is an open-access article distributed under the terms of the Creative Commons Attribution 4.0 International (CC BY 4.0) License.

Recibido/Received: 02/08/2024

Aceptado/Accepted: 23/09/2025

Publicado on-line/Published on-line: 22/01/2026

## 1. INTRODUCTION

3D point clouds have gained substantial recognition within the construction industry as an invaluable source of information. These point clouds find diverse applications such as 3D model reconstruction, safety management, building performance analysis, and construction progress tracking [1], [2].

A 3D point cloud is essentially a collection of data points within a 3D coordinate system, meticulously representing the surfaces of objects or environments. This versatility is made possible by the capacity of 3D point clouds to accurately represent the geometric characteristics of Cultural Heritage objects, including their dimensions, shapes, orientations, and positions. Within this field, point clouds find practical uses as the geometrical base for generating models for Historic Building Information Models, computational analysis, and the creation of built planimetries [3].

Although laser scanners are favoured for high-precision applications and photogrammetry is often chosen for its lower cost, the most commonly used resolution for Cultural Heritage documentation is 5 mm, as reported in the systematic review by Sánchez-Aparicio et al. 2023 [3].

Moreover, this use could be extended to the field of damage detection, particularly when exploiting the geometric and radiometric features of the captured data [4]. This question is highlighted in the recent literature review conducted by Sánchez-Aparicio et al. 2023 [3], showing the great potentiality of this information source in detecting deformations, settlements, moisture areas or crusts among other forms of damage. Examples of this potential can be found in the works performed by Sánchez-Aparicio et al. [4], Valero et al. [5] or Masiero and Costantino [6].

In contrast to the promising potential offered, the methodologies for damage detection currently require manual segmentation of the constructive elements to be carried out [3]. This issue has been identified as an area of potential future research in the literature review performed by Sánchez-Aparicio et al. [3]. Within this context it can find in the recent literature a plethora of studies that have addressed the constructive segmentation of 3D point clouds by employing Artificial Intelligence approaches [7]. A notable example of this capacity can be found in the study of the Milan Cathedral performed by Teruggi et al. [8]. In this work the authors propose the use of a Machine Learning algorithm (i.e., Random Forest classifier) to split the 3D point cloud into constructive elements. The results of this work are highly promising, as the methodology performs with remarkable accuracy, even in complex environments like the Cathedral.


Taking into consideration the current state of the art, the aim of this work is to develop a method capable of integrating Artificial Intelligence approaches for constructive segmentation and geometric-based methods for the automatic evaluation of deflections in historic timber floors. To validate the proposed strategy, the interior of the convent of Nuestra Señora de Gracia in Ávila (Spain) was chosen as a study case.

In this context, the paper is structured as follows: Section 2 defines the materials and methods used in this work, including the study case; Section 3 presents the results achieved through the application of the proposed methodology and, finally, Section 4 summarises the conclusions drawn from this research, along with further lines of work.

## 2. MATERIALS AND METHODS

### 2.1. Study case

The chosen case study is Nuestra Señora de Gracia convent in Avila, Spain. This historical architectural complex has been preserved since the 16th century and has undergone various modifications up to the 20th century. The construction follows a “U” shape layout, carefully adapted to the natural landscape. The building comprises load-bearing masonry walls and wooden floors, which are directly supported by the ground, except for one corridor that features arched brick galleries. For further details about the constructive disposition of this building the reader is encouraged to consult Villanueva-Llauradó et al. 2022 (Figure 1) [9].

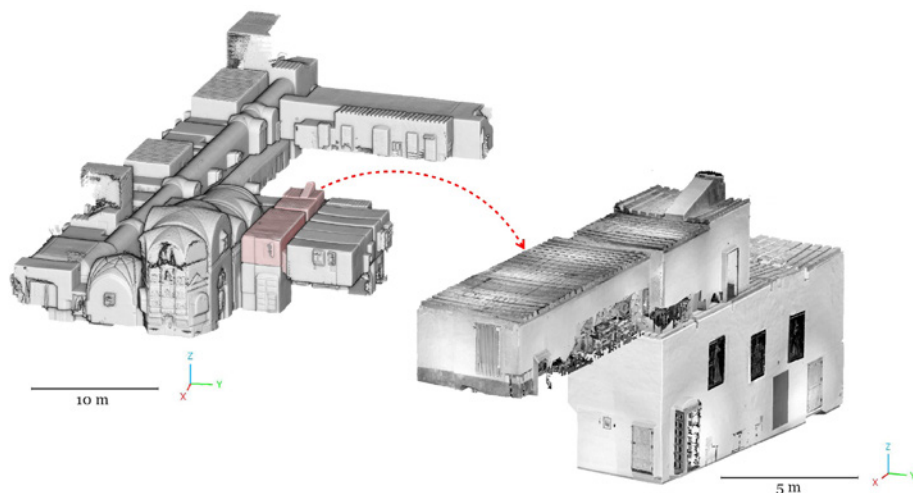

**Figure 1.** 3D point cloud of the convent Nuestra Señora de Gracia. The red zone highlights the area of interest for this study  
Adapted from Villanueva-Llauradó et al. 2022 [9] and Sánchez-Aparicio et al. 2023 [10].

The data employed in this study was extracted from a previous digitalization campaign in which part of the timber slabs were digitalized through the application of the terrestrial laser scanner Faro Focus 120 (Figure 1, 2) [9]. This LiDAR sensor employs the Amplitude Modulated Continuous Wave (AMCW) measurement principle, known for its high data acquisition rate and accuracy. Specifically, this sensor is capable of capturing between 120,000 to 976,000 points per second with a nominal accuracy of 2 mm.



Figure 2. Slabs of the convent Nuestra Señora de Gracia.

## 2.2. Methodology for evaluating the deflection of the beams

As previously outlined in the introduction, the primary objective of this research is to develop a methodology capable of exploiting the information contained in the 3D point cloud by combining Artificial Intelligence techniques with other point cloud processing methods. This methodology is summarized in the Figure 3.

The input of the methodology is the 3D point cloud acquired through Terrestrial Laser Scanner. This point cloud is a compilation of data from multiple scan stations that were aligned into a unique coordinate system. This input is pre-processed with the purpose of deleting extraneous elements such as people or ornamental motifs that were captured during the digitalization campaign. This phase also encompasses a sampling step to ensure uniform data density in the input. After that, a data processing stage is proposed. This stage includes features extraction (used for Artificial Intelligence training) as well as the classification of the data employing a Random Forest strategy. While not strictly required by the workflow, constructive sense is also employed to define the most appropriate search radii and geometric parameters for this study case. Finally, the methodology includes a deflection analysis that uses the data extracted from the previous stage as well as several point cloud processing algorithms to autonomously extract the deflection of the beams.

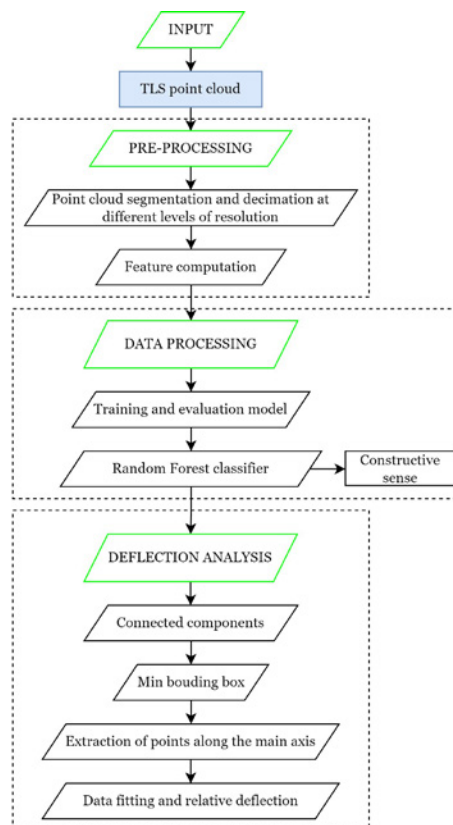


Figure 3. Scheme of the proposed workflow.

### 2.3. Data pre-processing


The initial step involves the preparation of the 3D point cloud for Artificial Intelligence segmentation. To this end, it is required to apply the following stages: i) removal of non-relevant areas; ii) subsampling, iii) data classification and iv) feature extraction. All these operations were carried out with the open-source software CloudCompare® (<https://www.cloudcompare.org>). During the first stage, it was decided to eliminate ornamental elements, furniture and any people captured during the data acquisition process. Subsequently, the subsampling and classification of the 3D point cloud were conducted. Both stages are mandatory in order to fulfil the final goal. The subsampling serves to homogenize the input data, while data classification provides semantics to the 3D point cloud, making it suitable for training and testing the Artificial Intelligence. They were implemented following the approach proposed by Teruggi et al. [8]. In this article the authors introduce a multi-level and multi-resolution subsampling and classification technique in contrast to the one-step (non-hierarchical) classification [11], [12], [13], which has been proven to enhance the efficacy of the Artificial Intelligence model.

The first level refers to the main structural framework of the different rooms within the Convent, defining a global functional segmentation of the entire dataset; categorizing it into floors, vertical walls and slabs. These macro-categories were achieved through point cloud processing at a 5 cm resolution.


The second level introduces a deeper definition by breaking down the macro-categories from the first level. In this case, the floor is divided into joists and wooden boards with a higher resolution level of 2 cm.

Finally, the third level involves the subcategorization of the previous level with a resolution of 1 cm. Therefore, the timber joists are subdivided into their scanned views, distinguishing between the base and sides of the joists. This detailed categorization will be useful for automatic joist deflection extraction.

It is worth noting that for training purposes, only classifying 25% of the entire scene is required [7]. However, in the context of this study it was made the choice was made to classify the entire scene within various resolution levels in order to assess the performance of the algorithm (Figure 4, 5, 6).

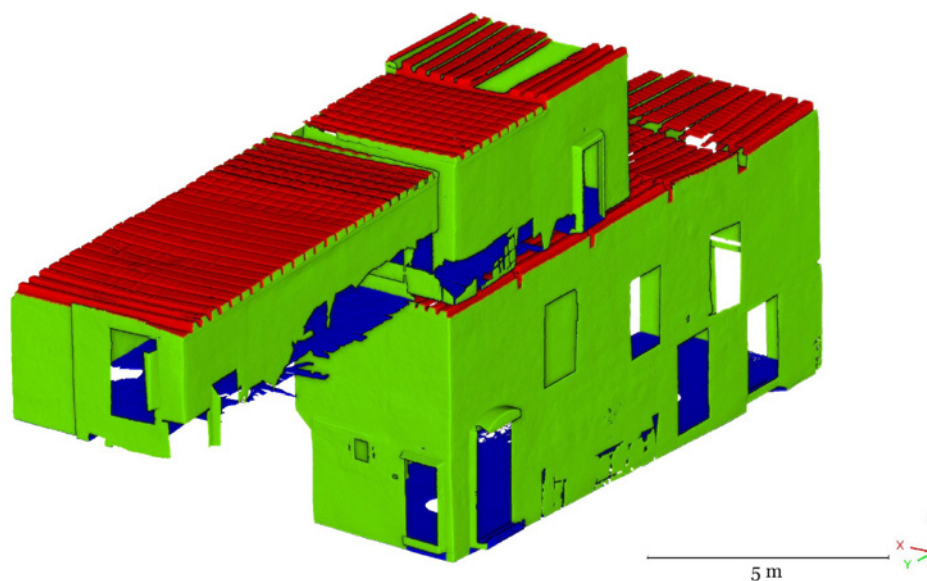


**Figure 4.** 3D point cloud segmented on first level of classification. The red color represents the class slabs. The blue color represents the class floors and the green represent the class vertical walls. This classification is carried out manually by the operator with the aim of evaluating the algorithm's behaviour.

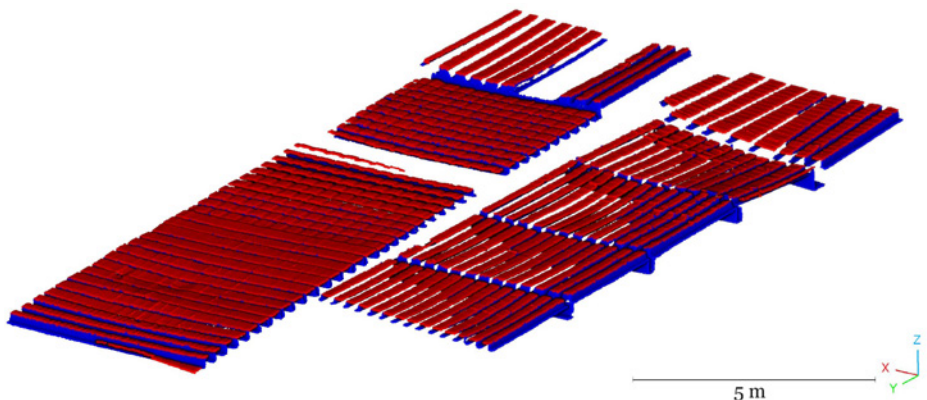

**Figure 5.** 3D point cloud segmented on second level of classification. The red color represents the class timber boards and the blue the timber joists. This classification is carried out manually by the operator with the aim of evaluating the algorithm's behaviour.




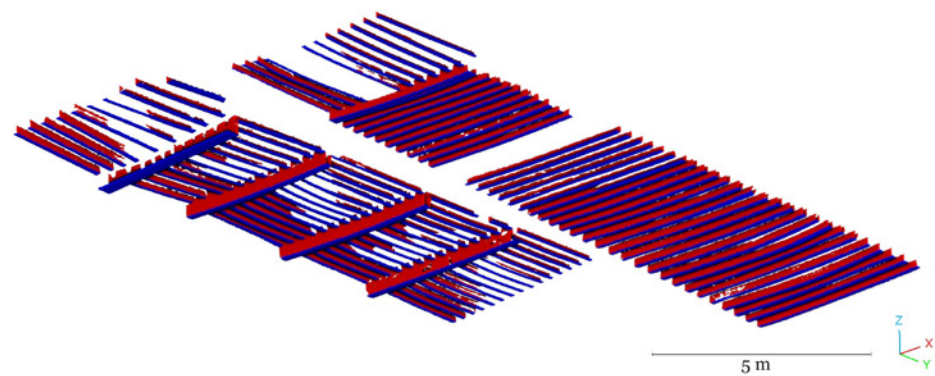

**Figure 6.** 3D point cloud segmented on third level of classification. The red represents the class joist faces and the blue the class joist edges. This classification is carried out manually by the operator with the aim of evaluating the algorithm’s behaviour.

2.3.1. Feature extraction

Feature extraction in the context of a 3D point cloud involves the process of adding new layers of information (features) to each point within the point cloud defining their local characteristics. The following parameters were used in this study: i) geometric features (roughness, mean curvature, gaussian curvature, normal change rate, sum of eigenvalues, omnivariance, eigenentropy, anisotropy, planarity, linearity, surface variation, sphericity and verticality) applying the feature equations defined in the work by Weinmann et al. [11], ii) the Z parameter, which differentiates the point cloud according to its location along the Z axis, iii) the relative position parameter, which divides the point cloud according to the laser scanner’s height (points above a certain height are assigned a value of 1, while points below are given a value of 0), and finally iv) the intensity parameter, which differentiates the point cloud according to its degree of intensity. It is worth noting that the feature extraction process requires the definition of an appropriate neighbour’s size. In this case a search radius (Figure 7) was employed with different range values assigned to each analysis level. Specifically, 0.1 to 1.6 meters for Level 1, 0.05 to 0.8 for Level 2 and 0.025 to 0.4 for Level 3. For more details on the significance and purpose of each level, the reader is referred to Section 2.3.

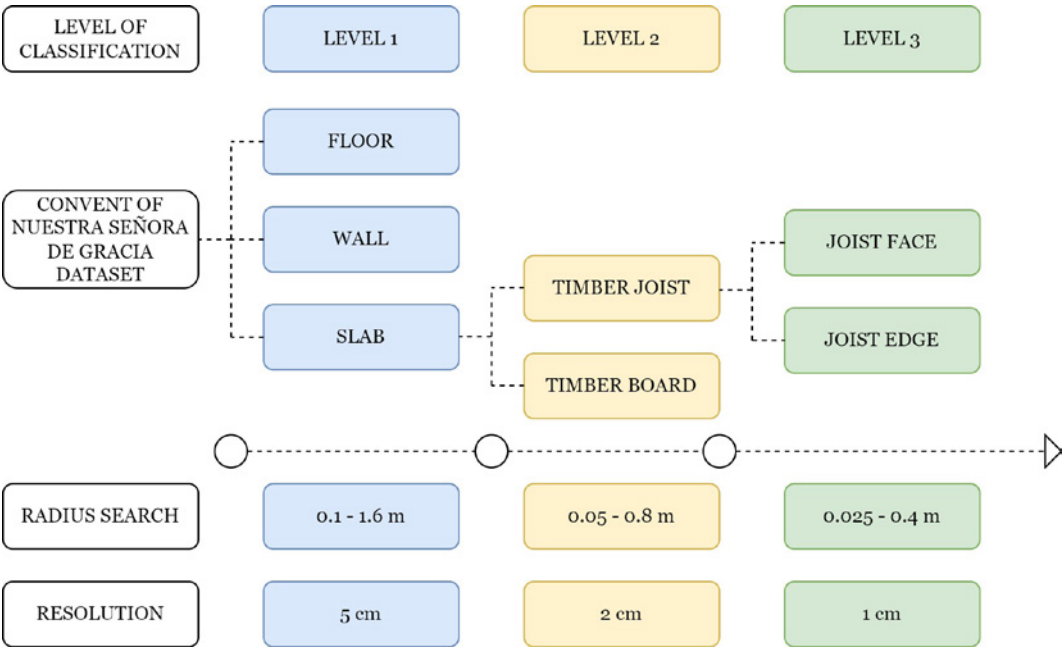

**Figure 7.** Scheme of the methodology used for classification.

2.4. Data processing

Artificial Intelligence Training can be understood as a process in which a model establishes a relationship between specific inputs (i.e., coordinates or features of the points) and the corresponding class assigned to each point. This process requires performing a multistage workflow, which can be summarized as follows: i) the train-evaluation splitting and ii) the classification.


2.4.1. Training and evaluation

In addition to extracting the geometrical features, a subset of the point cloud was manually divided to train the Artificial Intelligence algorithm at each classification level. In this study, less than 25% was allocated for the training model; while the remainder served to evaluate the algorithm’s performance.

The Figure 8 displays the training segment of the point cloud (colored) in comparison to the evaluation part (grey).

The final step of this stage comprises the automatic classification of the point cloud. To this end it was opted to employ a Machine Learning approach, specifically the Random Forest algorithm [14]. This algorithm is highly used in the literature as evidenced by the review performed by Yang et al. [7]. This method combines multiple decision trees to perform an accurate classification of input data. Its ability to handle complex and noisy datasets, as well as its resistance to overfitting, makes it a solid choice for this classification task.

In the present work, Python® scripts have been used to run the Random Forest, more specifically the library scikit-learn (<https://scikit-learn.org/stable/index.html>) was used. The count values for both accurate and erroneous predictions are condensed and presented within a confusion matrix, a specialized tabular format designed for visualizing the algorithm's performance. Within this matrix, individual rows correspond to predicted class instances, while each column corresponds to actual class instances. Moving on from the confusion matrix, three key metrics were utilized for each class: i) Precision, which gauges the level of precision or correctness, ii) recall, which evaluates the degree of comprehensiveness or completeness and iii) the F1-score, which harmonizes both precision and recall into a single metric. These strategies are commonly used in this type of works [8].

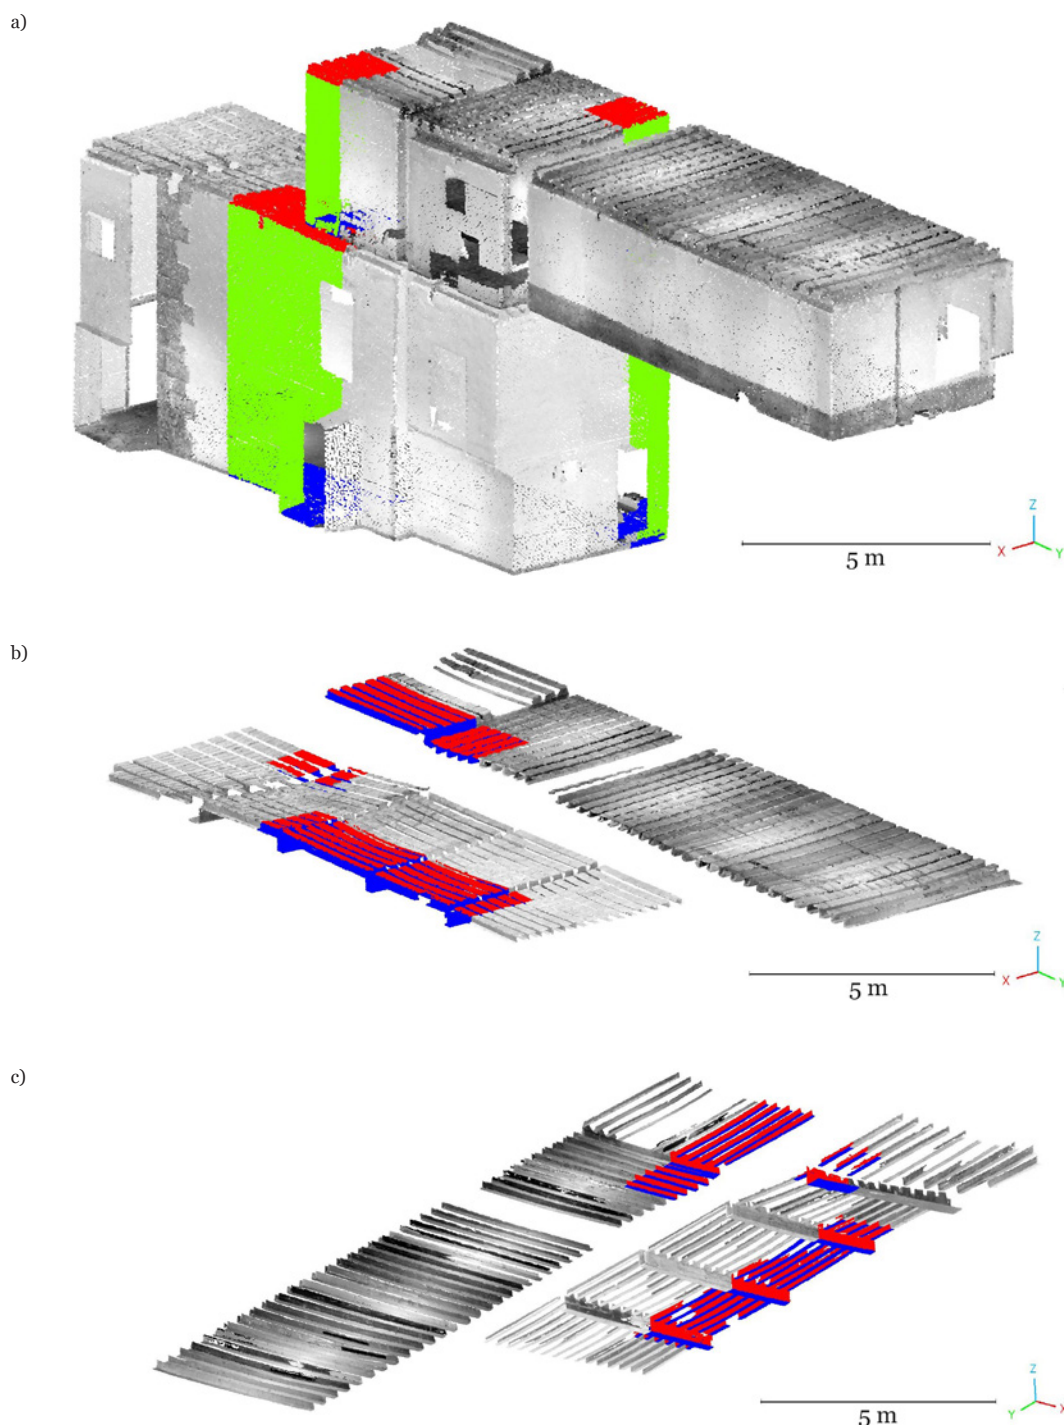

**Figure 8.** Train-evaluation splitting: a) Level 1, b) Level 2 and c) Level 3.


#### 2.4.2. Deflection analysis

The previous stage enabled us to give semantic to the 3D point cloud, facilitating its division into areas of interest, such as the bases of the joists. These bases comprise a set of points that can be processed to accurately determine the current deflection of these elements. To this end the following algorithms were applied (Figure 9): i) the Connected Components strategy; and ii) the Minimum Bounding Rectangle approach.

The first of the algorithms allows us to segment the class “joist edge” into individual elements. To this end the algorithm splits the 3D point cloud into 3D voxels with a predefined dimension. Then, the algorithm evaluates the connectivity of each voxel with its neighbours, allowing to split the 3D point cloud into elements that are separated by a specific distance.

At this stage of the process, we have extracted several 3D point clouds from the original one, each representing a joist edge. It is worth noting that from a geometrical point of view, the 2D projection of these edges can be represented as rectangles. Under this assumption, we decided to project the 3D point clouds of each joist onto the X-Y plane and subsequently apply the minimum bounding rectangle algorithm. This method enables the determination of the rectangle with the minimum area from a set of 2D points (x, y coordinates of the edges), whose main axis correspond with the desired axis of the joist.

The final step of this stage comprises the extraction of the deflection. In this sense, it is necessary to determine the length of the beam (length of the minimum bounding rectangle) as well as the maximum and minimum deflection (z-coordinate). The latter is only computed on those points that fall within a tolerance range from the main axis to enhance the process efficiency.

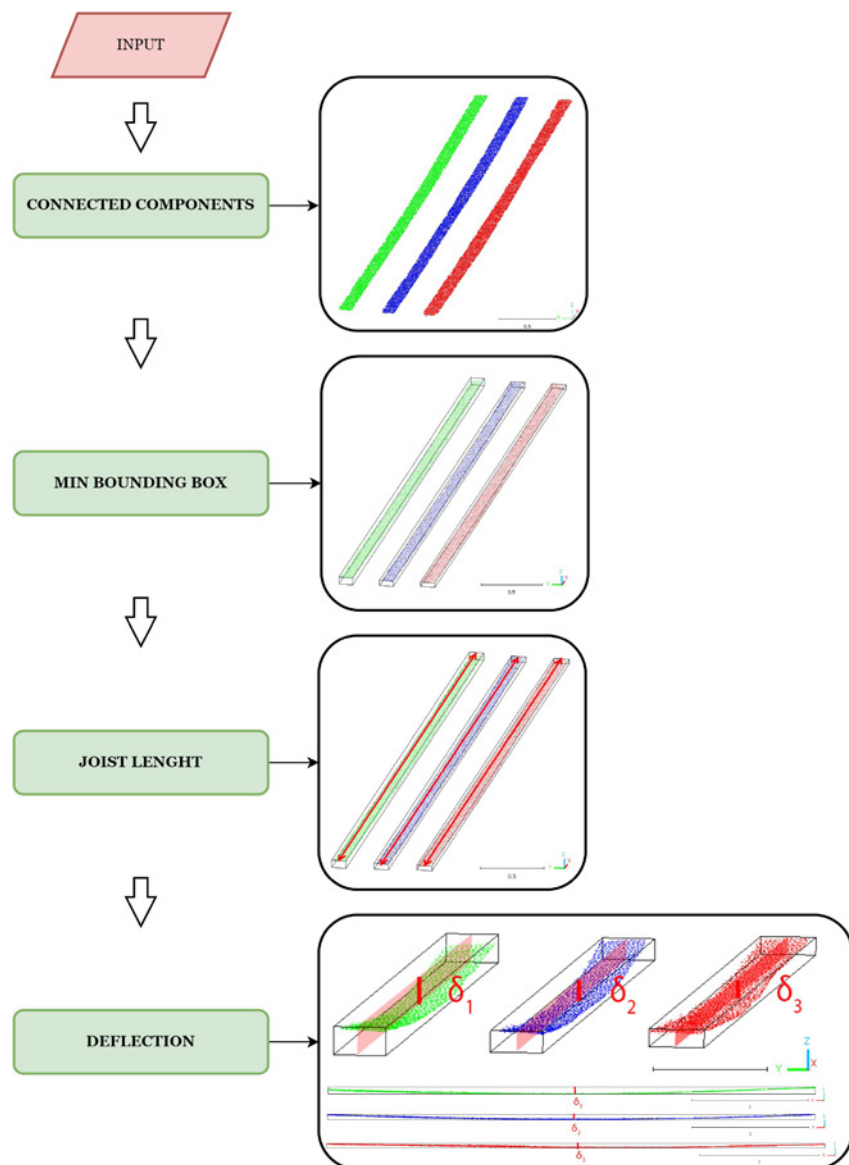

**Figure 9.** Scheme of the proposed deflection analysis.

The first step was performed in the open-source software CloudCompare®. Meanwhile the rest were computed by using an in-house Python script. Thanks to the data extracted, it becomes possible to compute the relative deflection (maximum drop of span with respect to the end of the part with the smallest span, divided by the span of the section) of each joist in accordance with Spanish guidelines for timber structures [15].




### 3. EXPERIMENTAL RESULTS

The following section will show, step-by-step, the results obtained in each one of the stages previously described.

#### 3.1. Pre-processing of the 3D point cloud

Firstly, elements that are not contextually relevant were removed, such as decorative motifs or individuals. Then, the 3D point cloud is subsampled at different resolution levels in accordance with Section 2.3.1. Finally, the features of the 3D point cloud were extracted using the point cloud processing software CloudCompare® (<https://www.cloudcompare.org>).

The following figures show part of the results obtained during the feature computation stage.

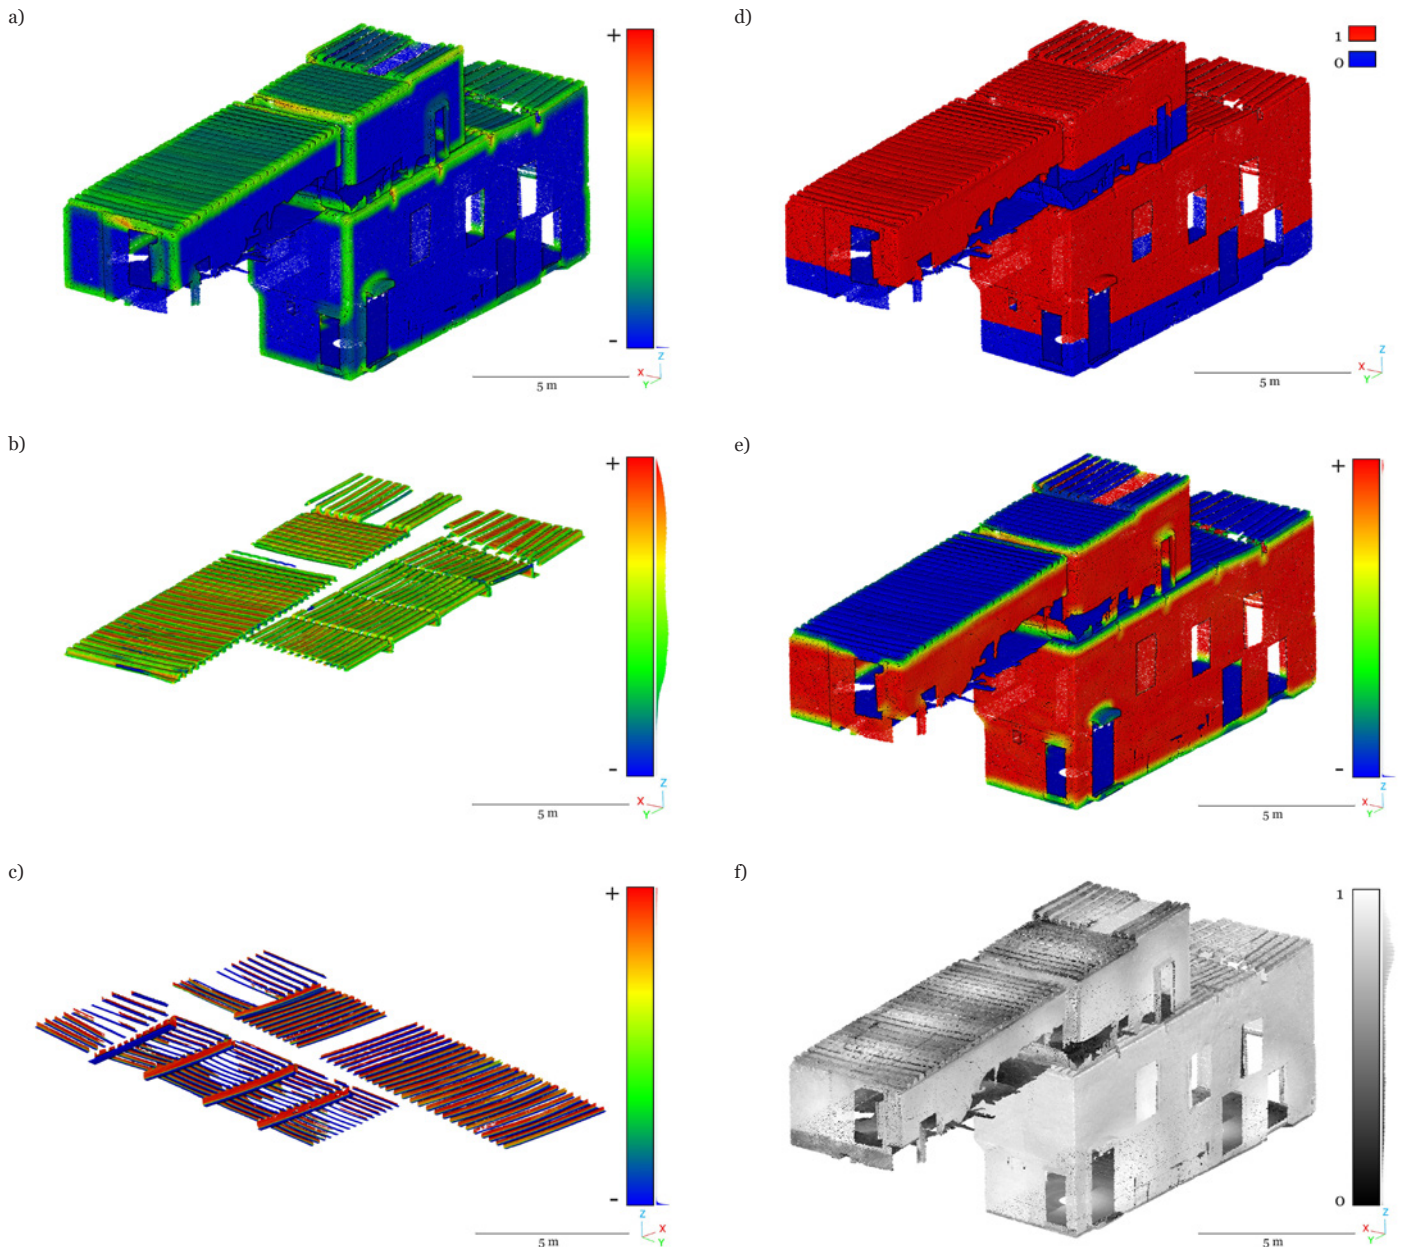

**Figure 10.** Feature computation results: a) Level 1 (Surface variation 0.4), b) Level 2 (Planarity 0.1), c) Level 3 (Verticality 0.05), d) Relative position, e) Verticality (1.6), and f) Intensity.

#### 3.2. Machine Learning predictions

As mentioned above, Random Forest has been performed on each level of the 3D point cloud, employing the enriched 3D point cloud as input (with the features previous showed). This step was carried out by using an ad-hoc script written in Python. The parameters used to run the Random Forest script were i) number of estimators (100,200), ii) maximum deep (none), iii) maximum number of features to take (square root), iv) bootstrap (false, true); as well as graphs to show results: i) Importance, ii) confusion matrix and iii) matrix classification matrix. The following tables and figures show the outcomes obtained during the application of the machine learning approach at various levels (Figures 11, 12, 13, 14 and Tables 1, 2, 3). This application has been carried out using Seg4D® software [16].



Table 1. Classification metrics at level 1

|                  | Precision (%) | Recall (%) | F1 Score (%) |
|------------------|---------------|------------|--------------|
| Floor            | 98.4          | 99.9       | 99.1         |
| Wall             | 99.2          | 98.4       | 98.8         |
| Slab             | 97.8          | 98.1       | 97.9         |
| Macro average    | 98.5          | 98.8       | 98.6         |
| Weighted average | 98.6          | 98.6       | 98.6         |

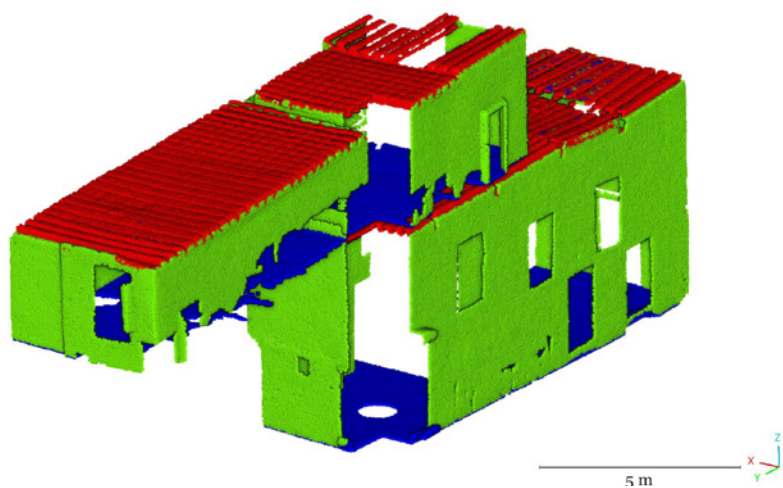


Figure 11. 3D point cloud of the prediction on first level of classification. The red points represent the slab class. The blue points the class floor and the green the class vertical walls.

Table 2. Classification metrics at level 2

|                  | Precision (%) | Recall (%) | F1 Score (%) |
|------------------|---------------|------------|--------------|
| Timber joist     | 97.9          | 97.9       | 97.9         |
| Timber deck      | 97.4          | 97.5       | 97.4         |
| Macro average    | 97.7          | 97.7       | 97.7         |
| Weighted average | 97.7          | 97.7       | 97.7         |

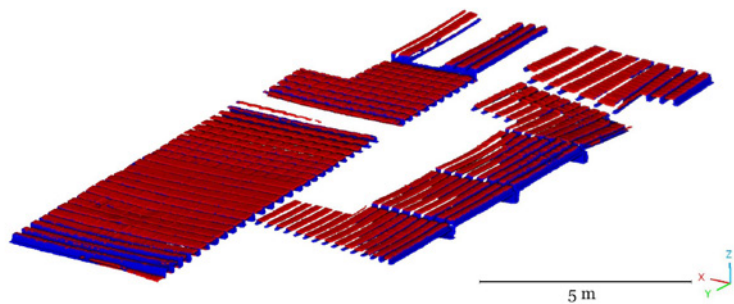


Figure 12. 3D point cloud of the prediction on second level of classification. The red points represent the class timber boards. The blue points represent the class timber joists.

Table 3. Classification metrics at level 3

|                  | Precision (%) | Recall (%) | F1 Score (%) |
|------------------|---------------|------------|--------------|
| Joist edge       | 99.2          | 99.0       | 99.1         |
| Joist face       | 99.3          | 99.4       | 99.4         |
| Macro average    | 99.2          | 99.2       | 99.2         |
| Weighted average | 99.3          | 99.3       | 99.3         |

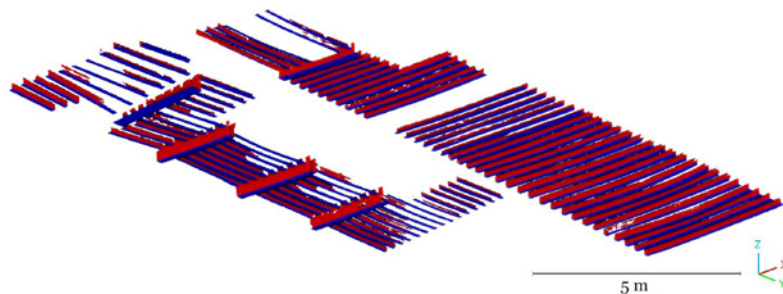


Figure 13. 3D point cloud of the prediction on third level of classification. The red points represent the joist face class. The blue points represent the joist edge class.

According to the previous figures and tables, the classification results show a precision of approximately 98.6% for Level 1, 97.7% for Level 2, and 99.3% for Level 3. These results are further examined and discussed in relation to the feature importance at each level (Figures 14, 15, and 16) in Section 3.3.



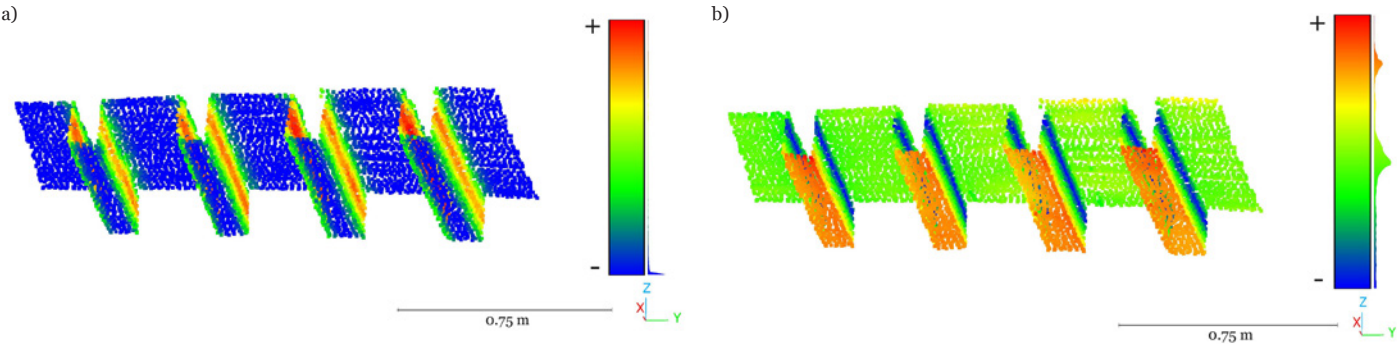


Figure 14. Features with great impact (importance) in the final classification: a) Verticality (0.1), b) Roughness (0.4).

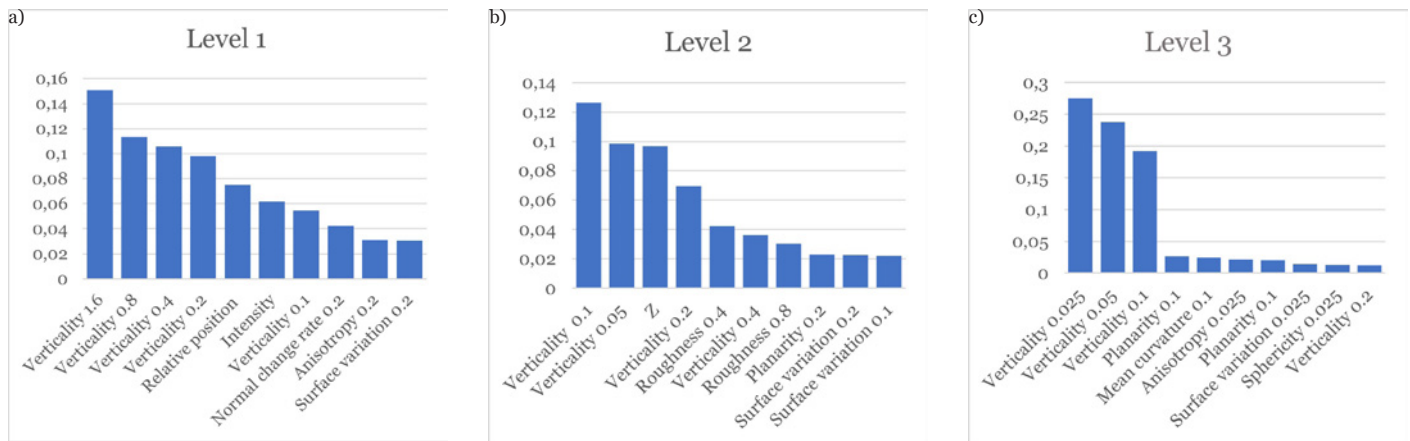


**Figure 15.** Feature importance results: a) Level 1, b) Level 2 and c) Level 3.

During each classification the impact of each feature on the results was analysed. To this end, it was decided to use the Feature Importance graph, ranking the features in accordance with their impact on the results. This impact was measured by using the Gini purity index [14]. The Figure 15 shows the results of this analysis. For a more detailed description clarifying the importance of the parameters at each level, readers should refer to Section 3.3.

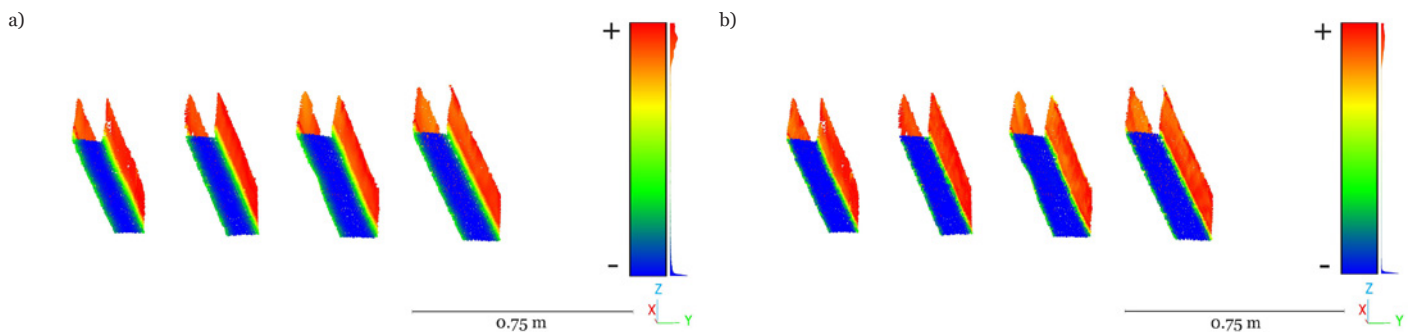

**Figure 16.** 3D point cloud of the best parameters for the Random Forest: a) Verticality (0.025), b) Verticality (0.05).

According to the evaluation metrics, the performance of the Random Forest classifier is close to perfection, showing minor mismatches in areas with great difficulty (i.e., beam attached to the wall) or regions with low data density (Figure 17). These mismatches required manually correction to ensure the proper deflection analysis of the beams.




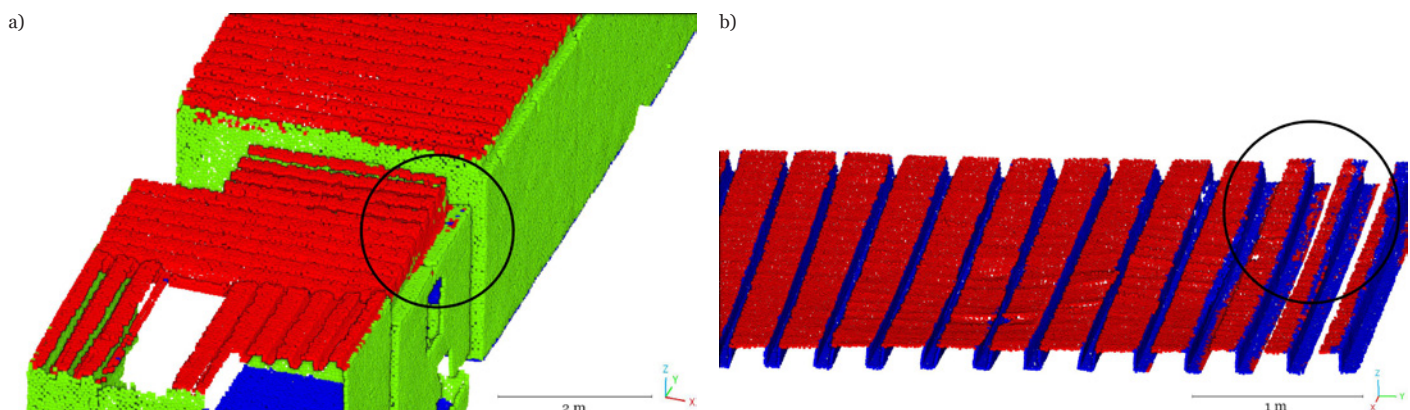


**Figure 17.** Mismatches of the Random Forest classification: a) Level 1, b) Level 2.

### 3.3. Constructive sense of the results obtained

The results of the feature importance analysis provide a general overview of the relevance of each feature (Figure 15). To summarise, the best parameters for classification were: i) the geometric features for all levels, in particular the verticality parameter, ii) the Z parameter for level 2, iii) the relative position for level 1 and iv) the intensity for level 1. This significance appears to be linked with certain constructive aspects of this type of slabs [17] (Table 4, 5, 6, 7).

**Table 4.** Relation between the search radii and the standard measurement.
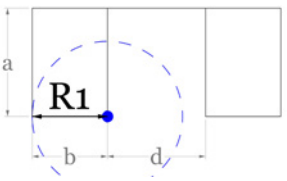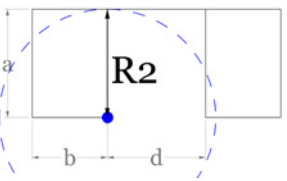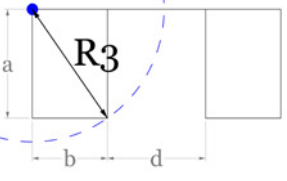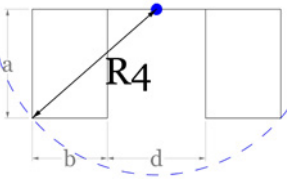
| Joists section detail and their respective search radii                            | Formula                                            | Standard length (mm) |
|------------------------------------------------------------------------------------|----------------------------------------------------|----------------------|
|   | $R1 = b$                                           | 104                  |
|   | $R2 = a$                                           | 139                  |
|   | $R3 = \sqrt{a^2 + b^2}$                            | 173,6                |
|  | $R4 = \sqrt{a^2 + \left(b + \frac{d}{2}\right)^2}$ | 267,9                |

**Table 5.** Justification of the best parameters for Level 1.

| Parameters           | Level 1                                                                                                                                                                                                                                                                                                               |
|----------------------|-----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|
| Geometrical Features | The Scalar Verticality is the best result, especially with radius 1.6 m, which determines the completely horizontal slab construction system. According to the radius calculations, verticality should be completely disregarded for floor slabs with a radius greater than 267.9 mm, i.e., if it is greater than R4. |
| Z parameter          | It leads to confusion between the floor of the upper storey and the slab below, as the two are very close together (150 - 250 mm).                                                                                                                                                                                    |
| Relative position    | More accurate than Z parameter, as it differentiates the floor from the slab into two distinct classes.                                                                                                                                                                                                               |
| Intensity            | This parameter obtains better results as all building systems are made of different materials.                                                                                                                                                                                                                        |

**Table 6.** Justification of the best parameters for Level 2.

| Parameters           | Level 2                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                   |
|----------------------|-----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|
| Geometrical Features | The best result is obtained with the smallest radius for Scalar Verticality, since a larger radius means less distinction between the horizontal and vertical planes that make up the slab. According to the radius calculations, to differentiate the joist from the timber board, the radius should be smaller than R3, i.e., less than 173.6 mm. A greater radius would mean that no point on the joist would recognise any other point on the joist within the same plane perpendicular to the joist. |
| Z parameter          | This parameter improves the prediction because the deck is above the joist.                                                                                                                                                                                                                                                                                                                                                                                                                               |
| Relative position    | It is disregarded since the entire point cloud of level 2 is above the scanner.                                                                                                                                                                                                                                                                                                                                                                                                                           |
| Intensity            | As both construction systems are made of the same material, this parameter does not improve the result.                                                                                                                                                                                                                                                                                                                                                                                                   |


**Table 7.** Justification of the best parameters for Level 3.

| Parameters           | Level 3                                                                                                                                                                                                        |
|----------------------|----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|
| Geometrical Features | The best result is obtained with the Scalar Verticality with a smaller radius, as a larger radius means less distinction between the vertical and horizontal plane that forms the joist.                       |
| Z parameter          | This parameter does not improve the prediction because the joists have an excessive deflection (subsequently calculated), which implies that many points of one class are in the same Z position as the other. |
| Relative position    | The same as in the Level 2.                                                                                                                                                                                    |
| Intensity            | The same as in the Level 2.                                                                                                                                                                                    |




### 3.4. Timber joist deflection

The final stage of the methodology comprised the automatic calculation of the beam's deflection. For this purpose, the "Joist edge" class as input was employed. This stage was computed by using an ad-hoc Python script following the steps defined in Figure 9. First, the beams were splitted by using the Connected Component algorithm. In this case the unique input value was the voxel resolution set at 1 cm, enabling the proper separation of elements (Figure 18).

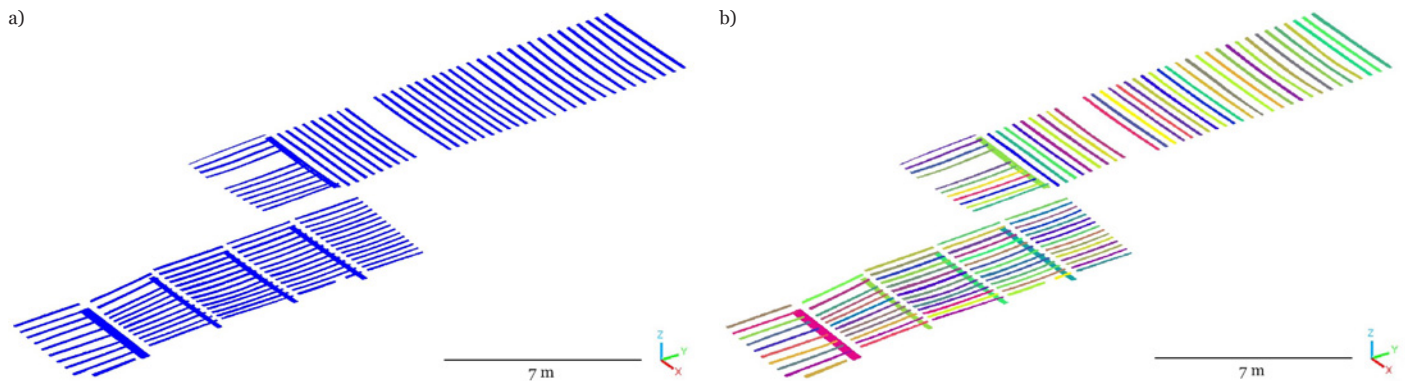

**Figure 18.** Results after applying the first step: a) original input; b) element clusterization by using the connected components algorithm.

Following this, the minimum bounding rectangle for each beam was computed to determine its main axis and calculate its length. Complementary to this value, the length, the maximum and minimum height within each beam were extracted. These values were plotted in a single graph with the aim of facilitating further structural works (Figure 19).

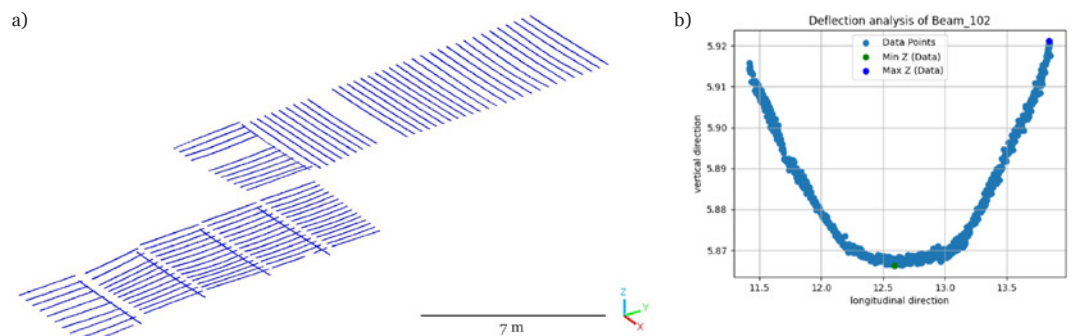


**Figure 19.** Results after applying the second step: a) extraction of the beam axis by using the Minimum Bounding Rectangle algorithm; b) example of the graph obtained in the beam number 102 (units expressed in metres).

To enhance the workflow of the inspector, the results of this deflection analysis were integrated into the original 3D point cloud by adding two new layers. One layer represents the maximum deflection on each beam, while the other layer plots the beams that fulfil the relative deflection ( $L/300$ ) threshold in green and those that do not meet the requirements in red (Figure 20).

It is possible to observe that most of the beams do not meet the relative threshold requirements. However, there are some beams for which deflection is not properly calculated due to their lack of perfectly horizontal alignment (Figure 20 b).

This aspect has been identified as a limitation of the current approach, as the deflection ( $L/300$ ) in those beams can no longer be calculated because it would correspond to an end instead of the centre of the beam.

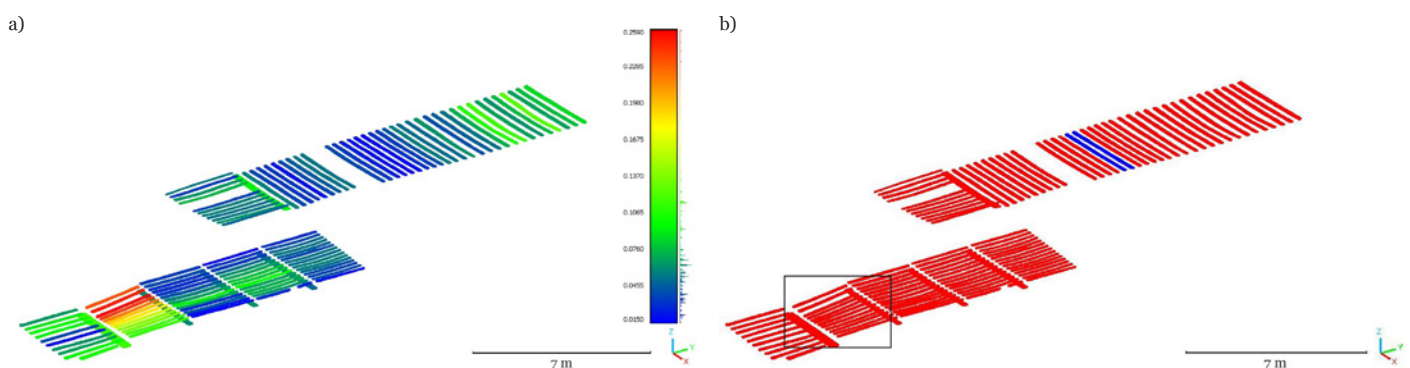

**Figure 20.** Results of the final 3D point cloud: a) with the maximum deflection layer (difference between the highest and the lowest point); b) with a layer that represents in blue the beams which meet the relative deflection ( $L/300$ ) threshold and in red those that don't fulfil this requirement (joists within the square was not properly calculated due to the impossibility of horizontal alignment).

#### 4. DISCUSSION OF THE RESULTS

This paper aims to present a methodology for the automatic evaluation of deflection in historic timber slabs. This methodology integrates Artificial Intelligence approaches for element segmentation and geometric-based methods for deflection parameters extraction.

On one hand, the results for element segmentation are highly promising, with accuracy values near to 100%. However, there are some classification mismatches that seem to be related to lack of data during the acquisition process, requiring manual fixing. In terms of processing time, it observes that the methodology performs efficiently (Table 8), running in just a couple of minutes on a system equipped with an i7 core processor, 16 Gb of RAM and a Graphical Computer Unit NVIDIA RTX A1000 6GB Laptop GPU. The most time-consuming stage is feature computation, as it involves extracting neighbourhood as well as geometric features (single value matrix analysis) for each point within various search radii, especially at higher levels of resolution.

**Table 8.** Processing time.

| Processing steps    | Level 1 | Level 2 | Level 3 |
|---------------------|---------|---------|---------|
| Subsampling         | 1       | 2       | 2       |
| Feature computation | 42      | 79      | 143     |
| Exporting as.xyz    | 2       | 4       | 9       |
| Random Forest       | 9       | 34      | 57      |
| Joist deflection    | -       | -       | 60      |
| Total               | 54      | 119     | 271     |

Values expressed in seconds.

On the other hand, the geometric-based methods used for extracting the deflections of the slabs allow us to obtain the parameters of great interest, such as the length of each beam and its deflection. In this case, the process required only 60 seconds to perform the analysis of 116 beams. However, two limitations that need improvement in future research were identified: i) the need for perfect classification of construction systems to perform in optimal conditions; and ii) the necessity of improving the deflection calculation in the case of non-horizontal beams. In this regard, minimal user intervention may be required to verify the accuracy of the results.

#### 5. CONCLUSIONS AND FUTURE WORKS

In accordance with the previous sections, it can be concluded that the proposed methodology shows a great potential for diagnosing timber slab floors as it seems to be robust and fast. However, it should be noted that this methodology is not entirely automatic due to the mismatches that could appear during the Random Forest classification. These mismatches are typically associated with areas lacking data density and points.

Therefore, effective data acquisition planning is essential to minimize these issues, including minimizing the presence of out-of-context elements since they require manual segmentation before applying the classifier. In terms of time efficiency, this methodology can save a substantial amount of time compared to manually measuring deflections, requiring just a few minutes to process the slabs used in this study.

Future works will focus on the following fields: i) further validation; ii) extension to other timber structures; iii) development of a tool able to integrate the process shown in this paper.

Regarding the first one, it has planned to apply this methodology to other study cases where a deflection analysis of timber structures is necessary. This will help to assess the replicability of the method.

Apart from this, it is required to extend this methodology to a wider range of timber elements, such as roof systems consisting of inclined rafters and trusses. In this sense, the incorporation of the Principal Component Analysis algorithm will be required to transition from inclined bases to horizontal ones and, consequently, implement the stages defined in the deflection analysis.

Finally, it has planned to develop an open-source tool that integrates this workflow within a unique software platform to make it more user friendly. To this end it will intend to develop a plugin for the open-source software CloudCompare® by utilizing a Python® wrapper for CloudCompare® (<https://github.com/tmontaigu/CloudCompare-PythonPlugin>).

#### ACKNOWLEDGMENTS

This work has been supported by the Community of Madrid and the Higher Polytechnic School of Madrid through the Project CAREEN (desarrollo de nuevos métodos basados en inteligencia Artificial para la caracterización de daños en construcciones históricas a través de nubes de puntos 3D) with reference APOYO-JOVENES-21-RCDT1L-85- SL9E1R. This work has been also partially funded by the Spanish Ministry of Science and Innovation through the grant CAS21/00557.

Pablo Sanz's pre-doctoral contract is part of grant PID2022-140071OB-C21, funded by MCIN/AEI/10.13039/501100011033 and ESF+.

#### DECLARATION OF COMPETING INTEREST

The authors of this article declare that they have no financial, professional or personal conflicts of interest that could have inappropriately influenced this work.

# AUTHORSHIP CONTRIBUTION STATEMENT

**Pablo Sanz Honrado:** Data curation, Writing – review & editing.

**Rubén Santamaría Maestro:** Data curation, Writing – review & editing.

**Jose Ramón Aira Zunzunegui:** Writing – review & editing.

**Paula Villanueva Llauradó:** Writing – review & editing.

**Luis Javier Sánchez Aparicio:** Funding acquisition, Supervision.

## REFERENCES

- [1] K. Mirzaei et al., “3D point cloud data processing with machine learning for construction and infrastructure applications: A comprehensive review”, *Advanced Engineering Informatics*, vol. 51, Jan. 2022, doi: 10.1016/j.aei.2021.101501.
- [2] Q. Wang and M. K. Kim, “Applications of 3D point cloud data in the construction industry: A fifteen-year review from 2004 to 2018,” *Advanced Engineering Informatics*, vol. 39, pp. 306–319, Jan. 2019, doi: 10.1016/j.aei.2019.02.007.
- [3] L. J. Sánchez-Aparicio et al., “Detection of damage in heritage constructions based on 3D point clouds: A systematic review,” *Journal of Building Engineering*, vol. 77, Oct. 2023, doi: 10.1016/j.jobbe.2023.107440.
- [4] L. J. Sánchez-Aparicio, S. Del Pozo, L. F. Ramos, A. Arce, and F. M. Fernandes, “Heritage site preservation with combined radiometric and geometric analysis of TLS data,” *Automation in Construction*, vol. 85, pp. 24–39, Jan. 2018, doi: 10.1016/j.autcon.2017.09.023.
- [5] E. Valero, A. Forster, F. Bosché, E. Hyslop, L. Wilson, and A. Turmel, “Automated defect detection and classification in ashlar masonry walls using machine learning,” *Automation in Construction*, vol. 106, Oct. 2019, doi: 10.1016/j.autcon.2019.102846.
- [6] A. Masiero and D. Costantino, “TLS for detecting small damages on a building façade,” *The International Archives of the Photogrammetry, Remote Sensing and Spatial Information Sciences*, vol. XLII-2/W11, pp. 831–836, May 2019, doi: 10.5194/isprs-archives-XLII-2-W11-831-2019.
- [7] S. Yang, M. Hou, and S. Li, “Three-dimensional point cloud semantic segmentation for cultural heritage: A comprehensive review,” *Remote Sensing (Basel)*, vol. 15, no. 3, Feb. 2023, doi: 10.3390/rs15030548.
- [8] S. Teruggi, E. Grilli, M. Russo, F. Fassi, and F. Remondino, “A hierarchical machine learning approach for multi-level and multi-resolution 3D point cloud classification,” *Remote Sensing*, vol. 12, no. 16, p. 2598, Aug. 2020, doi: 10.3390/rs12162598.
- [9] P. Villanueva Llauradó et al., “A comparative study between a static and a mobile laser scanner for the digitalization of inner spaces in historical constructions,” in *Proc. REHABEND Int. Conf. Construction Pathology, Rehabilitation Technology and Heritage Management*, 2022, pp. 2492–2498.
- [10] L. J. Sánchez-Aparicio et al., “Evaluation of a SLAM-based point cloud for deflection analysis in historic timber floors,” *The International Archives of the Photogrammetry, Remote Sensing and Spatial Information Sciences*, vol. XLVIII-M-2–2023, pp. 1411–1418, Jun. 2023, doi: 10.5194/isprs-archives-XLVI-II-M-2-2023-1411-2023.
- [11] K. Zhang, S. Teruggi, Y. Ding, and F. Fassi, “A multilevel multiresolution machine learning classification approach: A generalization test on Chinese heritage architecture,” *Heritage*, vol. 5, no. 4, pp. 3970–3992, Dec. 2022, doi: 10.3390/heritage5040204.
- [12] D. Billi et al., “Machine learning and deep learning for the built heritage analysis: Laser scanning and UAV-based surveying applications on a complex spatial grid structure,” *Remote Sensing (Basel)*, vol. 15, no. 8, Apr. 2023, doi: 10.3390/rs15081961.
- [13] M. Russo, E. Grilli, F. Remondino, S. Teruggi, and F. Fassi, “Machine learning for cultural heritage classification,” in *Representation Challenges: Augmented Reality and Artificial Intelligence in Cultural Heritage and Innovative Design Domain*, Milan, Italy: FrancoAngeli, 2021, doi: 10.3280/oa-686.33.
- [14] M. Pal, “Random forest classifier for remote sensing classification,” *International Journal of Remote Sensing*, vol. 26, no. 1, pp. 217–222, Jan. 2005, doi: 10.1080/01431160412331269698.
- [15] Ministerio de Fomento, *Documento Básico SE-M. Seguridad estructural. Madera*, 2019.
- [16] L. J. Sánchez-Aparicio, R. Santamaría-Maestro, P. Sanz-Honrado, P. Villanueva-Llauradó, J. R. Aira-Zunzunegui, and D. González-Aguilera, “A holistic solution for supporting the diagnosis of historic constructions from 3D point clouds,” *Remote Sensing (Basel)*, vol. 17, no. 12, p. 2018, Jun. 2025, doi: 10.3390/rs17122018.
- [17] F. Lasheras Merino, “Patología de la construcción madera,” in *Tratado Técnico Jurídico de la Edificación y el Urbanismo. Tomo I. Patología de la Construcción y Técnicas de Intervención*, Thomson Reuters Aranzadi, 2009, pp. 789–850. [Online]. Available: <http://oa.upm.es/53437/1/Lo32009TCXIMadera.pdf>